
НҮҮРСНИЙ ОВООЛГЫН ҮЗҮҮЛЭЛТ

№ ETT_SP_CC



ISO 45001:2018



ISO 9001:2015



ISO 14001:2015



НИЙТ ЧИЙГ (ar)

3.0%

(-1.5; +1.5)

ҮНСЛЭГ (db)

15.0%

(-3.0; +3.0)

ДЭГДЭМХИЙ (daf)

≤28.0%

НИЙТ ХҮХЭР (db)

1.0%

(-0.3; +0.5)

БАРЬЦАЛДАХ
ЧАНАР

≥70.0

НҮҮРСНИЙ
ХЭМЖЭЭ

64.0

МЯН.ТН

ALS GROUP LLC
Mongol Nekhmei Building, 2nd khoroos
Chinggis Avenue, Khan-Uul District
Ulaanbaatar, Mongolia
Tel +976 70 007667



CLIENT:	Erdene Tavan Tolgoi JSC
ADDRESS:	Finance Center, Jigjidjav-8 1st khoroo, Chingeltei District Ulaanbaatar, Mongolia
ATTN:	Galtzaya.B
PROJECT NO.	xxx
LAB. JOB NO.	25117,19,129,136-TT
NO. SAMPLES:	8
Notes/Comments:	xxx


SAMPLES RECEIVED: 10/12/2025 11/12/2025
INSTRUCTIONS RECEIVED: 10/12/2025 11/12/2025
DATE OF REPORT: 11/12/2025 12/12/2025
STATUS OF REPORT: FINAL
ANALYSIS COMPLETE: 11/12/2025 12/12/2025
PREPARATION CODE: CSPSC, CSPSC, CSPG
ANALYSIS CODE: 1.2 COOKING COAL
 TM, MOIS, ASH, VOL,
 TSUL, CSN, CAIN
APPROVED BY: 
 Quality Manager
CHECKED BY: Chief Chemist

The test results are representative only of the sample received in the laboratory.

STANDARD METHOD		AS RECEIVED BASIS										AIR DRIED BASIS					DRY BASIS					DRY, ASH-FREE BASIS						
		GB/T 211	GB/T 212	GB/T 212	ISO 15979	GB/T 212	GB/T 212	GB/T 212	GB/T 212	ISO 15979	GB/T 212	GB/T 212	GB/T 212	ISO 15979	GB/T 212	GB/T 212	GB/T 212	ISO 15979	GB/T 212	GB/T 212	ISO 15979	GB/T 5448	GB/T 5447					
LAB NO.	SAMPLE NO.	Total Moisture (TM)	Ash (ASH)	Volatile Matter (VOL)	Fixed Carbon	Total Sulphur (TSUL)	Moisture (MOIS)	Ash (ASHB)	Volatile Matter (VOLL)	Fixed Carbon	Total Sulphur (TSUL)	Ash (ASHA)	Volatile Matter (VOL)	Fixed Carbon	Total Sulphur (TSUL)	Ash (ASHF)	Volatile Matter (VOL)	Fixed Carbon	Total Sulphur (TSUL)	Volatile Matter (VOL)	Fixed Carbon	Total Sulphur (TSUL)	Crucible Swelling Number (CSN)	Coal Caking Index (CKIN)				
																								5:1	3:3			
							%																					
1	ETT-SP-10336-1A	2.70	12.21	22.50	62.60	0.87	0.65	12.47	22.97	63.91	0.89	12.55	23.31	64.33	0.90	26.44	73.56	1.02	6.0	7.4	-	-	-	-				
2	ETT-SP-10336-1B	2.71	12.22	22.50	62.78	1.16	0.61	12.42	23.16	63.80	1.18	12.49	23.12	64.20	1.19	26.64	73.56	1.36	6.0	7.4	-	-	-	-				
3	ETT-SP-10336-2A	2.86	11.26	22.91	62.97	0.54	0.65	11.53	23.44	63.55	1.40	12.53	23.44	64.82	0.55	27.33	64.82	0.55	7.8	-	-	-	-	-				
4	ETT-SP-10336-2B	2.81	11.58	23.19	62.41	0.76	0.68	11.84	23.70	63.78	0.77	11.92	23.86	64.22	0.78	27.09	72.91	0.88	6.5	83	-	-	-	-				
5	ETT-SP-10336-3A	2.74	13.41	23.77	60.09	0.72	0.56	13.71	24.30	61.43	0.73	13.29	24.44	61.78	0.74	28.34	71.66	0.65	6.5	81	-	-	-	-				
6	ETT-SP-10336-3B	1.99	10.59	24.29	63.13	0.60	0.55	10.75	24.65	64.06	0.61	10.81	24.78	64.51	0.61	27.79	72.21	0.69	7.0	85	-	-	-	-				
7	ETT-SP-10336-4A	5.24	11.37	22.74	60.65	0.72	0.74	11.52	21.87	62.21	0.75	11.62	22.13	62.98	0.75	27.27	72.98	0.80	6.5	89	-	-	-	-				
8	ETT-SP-10336-4B	5.23	11.69	22.65	60.32	0.74	0.76	12.25	23.93	63.07	0.78	12.34	24.11	63.55	0.78	27.51	72.47	0.82	7.0	89	-	-	-	-				

QUALITY ASSURANCE/QUALITY CONTROL DATA

STDALWS-10/23	ASH	VOL	TSUL
Certified Value	10.67	20.55	0.620
Standard Deviation	0.056	0.137	0.0144
Unit	%	%	%
Analyzed value	10.69	20.60	0.618

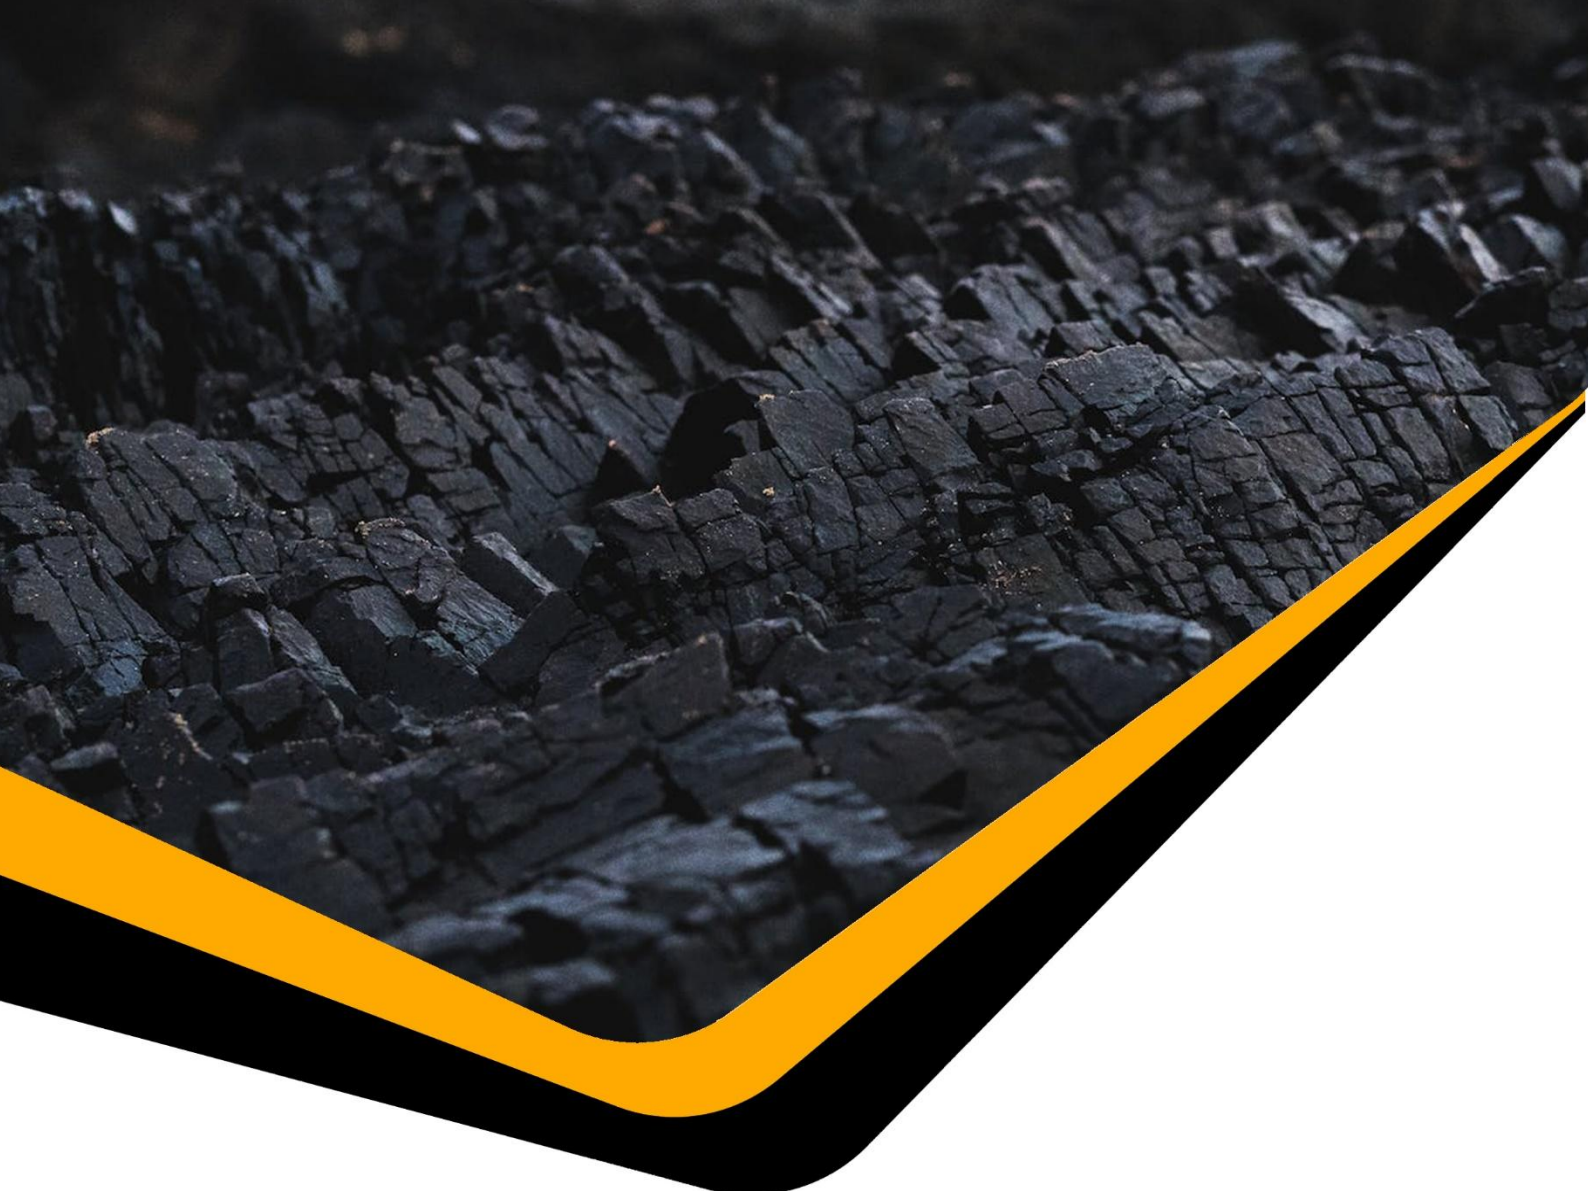

ISO 45001:2018



ISO 9001:2015



ISO 14001:2015



www.ett.mn



75055555
1800-1072



Финанс төв, 1-р хороо,
Чингэлтэй дүүрэг,
Улаанбаатар хот

